

Electronic properties of bulk and thin film SrRuO₃: a search for the metal-insulator transition

James M. Rondinelli,¹ Nuala M. Caffrey,² Stefano Sanvito,² and Nicola A. Spaldin^{1,*}

¹*Materials Department, University of California, Santa Barbara, CA, 93106-5050, USA*

²*School of Physics and CRANN, Trinity College, Dublin 2, Ireland*

(Dated: June 8, 2008)

We calculate the properties of the 4d ferromagnet SrRuO₃ in bulk and thin film form with the aim of understanding the experimentally observed metal to insulator transition at reduced thickness. Although the spatial extent of the 4d orbitals is quite large, many experimental results have suggested that electron-electron correlations play an important role in determining this material's electronic structure. In order to investigate the importance of correlation, we use two approaches which go beyond the conventional local density approximation to density functional theory (DFT): the local spin density approximation + Hubbard U (LSDA+ U) and the pseudopotential self-interaction correction (pseudo-SIC) methods. We find that the details of the electronic structure predicted with the LSDA do not agree with the experimental spectroscopic data for bulk and thin film SrRuO₃. Improvement is found by including electron-electron correlations, and we suggest that bulk orthorhombic SrRuO₃ is a *weakly strongly-correlated* ferromagnet whose electronic structure is best described by a 0.6 eV on-site Hubbard term, or equivalently with corrections for the self-interaction error. We also perform *ab initio* transport calculations that confirm that SrRuO₃ has a negative spin polarization at the Fermi level, due to the position of the minority Ru 4d band center. Even with correlations included in our calculations we are unable to reproduce the experimentally observed metal-insulator transition, suggesting that the electronic behavior of SrRuO₃ ultra-thin films might be dominated by extrinsic factors such as surface disorder and defects.

PACS numbers: 71.20.-b, 79.60.Dp, 79.60.-i, 32.10.Dk

I. INTRODUCTION

Conductive oxides are essential components in composite oxide heterostructures where they are often used as electrode materials in thin film applications.^{1,2,3} In the perovskite crystal family (ABO_3 stoichiometry), the itinerant ferromagnetic SrRuO₃ (SRO) is a popular choice since it is one of the more conductive metallic oxides with good thermal properties.⁴ In thin films, SRO is intensely investigated as a possible route to the realization of novel field-effect devices.^{5,6} In addition, it is of particular interest to the spintronic^{7,8} and multiferroic^{9,10} communities, which have been recently energized by the possible device applications available from engineering interface phenomena.^{11,12,13,14,15,16,17} However, one limitation in the design of thin film oxide devices is the observation of increased resistivity in metal oxides as the film thickness decreases. Such behavior is clearly present in ultra-thin films of SrRuO₃, where a metal-to-insulator (MI) transition¹⁸ occurs at four monolayers. This substantial change in the electrical conductivity presents a serious challenge for device miniaturization. In this work we explore the underlying physics of the thin film MI transition, which to date remain to be understood.

The 3d transition metal oxides (TMOs) are known to possess strong electron-electron correlation effects that can drive a system that should be metallic within a simple band picture into an insulating state. Due to the large spatial extent of the 4d-orbitals in the ruthenates, correlation effects are anticipated to be less important as stronger hybridization pro-

vides more effective screening and a reduced Hubbard U (Coulomb repulsion energy). Many experimental studies have already addressed the degree of electron-electron correlation in SrRuO₃ including X-ray and ultraviolet photoemission spectroscopy,^{18,19,20,21} specific heat measurements,²² infrared and optical conductivity measurements,²³ and transport experiments.²⁴ For example, Kim and coworkers¹⁹ use X-ray photoemission spectroscopy (XPS) to identify how such correlations change within the ruthenate family, and Toyota *et al.*¹⁸ use photoemission spectroscopy (PES) to detail the metal-insulator transition in SrRuO₃ as a function of film thickness concomitant with the onset of magnetism. In all of these studies, the general consensus is that electron correlation effects *do* play a role in determining the electronic structure of this itinerant ferromagnet, but to what degree remains unclear. Furthermore, some theoretical investigations have begun examining covalency,²⁵ correlation²⁶ and orbital ordering²⁷ effects in bulk SrRuO₃. The magnetic properties of SRO under epitaxial strain have also been investigated with first-principles techniques.²⁸

In this work, first-principles density functional theory (DFT) calculations are performed, first to identify the degree of correlation in bulk SRO, and second to investigate the driving force for the metal-insulator transition in ultra-thin films. We use two approaches to introduce correlation effects into the conventional band theory (local spin density) approach for treating the Ru 4d-orbitals and their hybridization with O 2p-orbitals: the local spin density + Hubbard U (LSDA+ U), and the pseu-

dopotential self-interaction corrected (pseudo-SIC) local spin density methods. In addition we investigate two structural variants – the ideal cubic perovskite structure and the experimentally observed orthorhombic structure, which includes tiltings and rotations of the RuO_6 octahedra. By comparing the results that we obtained for both methods and both structure types, we are able to comment on the nature of the metal-insulator transition in ultra-thin films.

II. CRYSTAL STRUCTURE & MAGNETISM

The perovskite class of materials is described by a network of corner-sharing BO_6 octahedra, in which the A -site cation is located at the center of a cube defined by eight BO_6 units. The ideal perovskite is cubic (space group $Pm\bar{3}m$), however several modifications exist owing to the range of cation sizes that can be accommodated in the structure. Deviations from the ideal cubic structure are defined by the Goldschmidt tolerance factor

$$t' = \frac{R_A + R_O}{\sqrt{2}(R_B + R_O)},$$

where R_i is the radius of atom i , and can be attributed to the requirement to optimize the anion coordination about the A -site cation.²⁹ Using the Shannon-Prewitt radii for this compound, a predicted tolerance factor of $t'=0.908$ is found, which is far from the ideal case $t'=1$, suggesting that distortions should occur.

Indeed, SRO undergoes a series of structural transformations with temperature, from high symmetry cubic ($Pm\bar{3}m$, stable above 950 K) to tetragonal ($I4/mcm$, stable between 820 K and 950 K) to distorted orthorhombic structure ($Pbnm$) at low temperatures. The orthorhombic distortion from the ideal cubic can be described by the tilting of the RuO_6 octahedra in alternate directions away from the c axis, and the rotation of the octahedra around the b axis; in both cases adjacent octahedra distort in the opposite sense (Figure 1). The degree of tilting and rotation (as defined in Fig. 1) of the octahedra are useful in describing the distortions in the oxygen network from the perfect cubic case. A rotation angle of 7.56° and a tilting angle of 10.47° (corresponding to a Ru-O-Ru angle of 159°) are found for $Pbnm$ SrRuO_3 . The structural changes reduce the hybridization between the Ru $4d$ states and O $2p$ states and lead to a narrowing of the bandwidths (see Section IV) compared with the ideal cubic case. Consequently the degree of correlation, described by U/W where W is the valence bandwidth, is expected to be enhanced.

Below approximately 160 K, SrRuO_3 exhibits strong ferromagnetic behavior, and has a measured Rhodes-Wohlfarth ratio³⁰ ($\mu_{\text{eff}}/\mu_{\text{sat}}$) of 1.3 suggesting that its magnetism can be well described by a localized d -electron model similar to the elemental ferromagnetic metals. Within this model and under an octahedral crystal field,

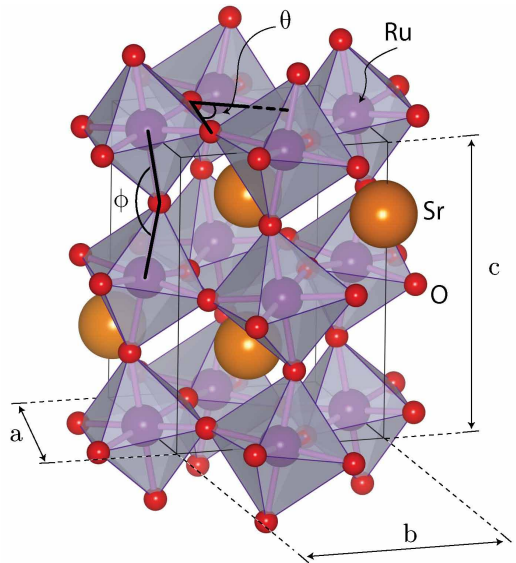


FIG. 1: (Color online) The orthorhombic ($Pbnm$) crystal structure of SrRuO_3 . The unit cell contains four formula units (f.u.) of the ideal cubic perovskite ($Pm\bar{3}m$). The structure is stabilized by shortening the Sr-O distance followed by a cooperative distortion of the RuO_6 octahedra to reduce the coordination volume of the Sr ions; this results in a smaller Ru-O-Ru bond angle, which in turn decreases the Ru $4d$ bandwidth and metallicity. The deviation in the structure from the high symmetry cubic state can be quantified using the tilting angle $(180^\circ - \phi)/2$ and the rotation angle $(90^\circ - \theta)/2$ of the oxygen octahedra.

the $4d$ -manifold splits into a threefold degenerate t_{2g} sub-band that is lower in energy than the twofold degenerate e_g band. Neglecting covalency, we would expect a spin-only magnetic moment of $2 \mu_B$, corresponding to a low-spin state for the Ru^{4+} ions ($d^4 : t_{2g}^3, t_{2g1}^1$). Experimentally, however, the moment is measured to be closer to $1.1 \mu_B/\text{f.u.}$, although values ranging from $0.9 \mu_B/\text{f.u.}$ and $1.6 \mu_B/\text{f.u.}$ have also been reported.³¹ (The spread in values is attributed to the large magnetocrystalline anisotropy of the material, and the difficulty in making large single-domain samples.) First-principles calculations also report a magnetic moment ranging from $0.9 \mu_B/\text{f.u.}$ to $2.0 \mu_B/\text{f.u.}$ ^{22,32,33,34} The reduced calculated magnetic moment in the solid compared to that in the free ion limit is due in part to the large spatial extent of the Ru $4d$ orbitals, which results in a significant overlap (hybridization) with the oxygen $2p$. Furthermore, due to the metallic character of SRO, an overlap of the majority and minority Ru $4d$ bands occurs at the Fermi level; as a result partial occupation of the minority band also leads to a reduced magnetic moment.

In this work, we examine the LSDA and “beyond-LSDA” electronic and magnetic properties of both the $Pbnm$ and $Pm\bar{3}m$ crystal variants. Metallicity and magnetism are both related to the d -bandwidth, which in turn depends on both correlations and structural properties such as tiltings and rotations of the oxygen oc-

tahdera. Our goal, therefore, is to identify the relative contributions of electron-electron correlation effects and structural distortions in driving the metal-insulator transition in SrRuO₃ thin films.

III. THEORETICAL METHODS

A. LSDA

Our initial electronic band structure calculations were performed within the local spin density approximation³⁵ (LSDA) using both the SIESTA^{36,37,38} and VASP^{39,40} density functional theory (DFT) packages. In each method we used the Perdew-Zunger⁴¹ parametrization of the Ceperley-Alder data⁴² for the exchange and correlation (XC) functional.

The core and valence electrons were treated with the projector-augmented-wave (PAW) method⁴³ for all calculations performed with VASP.⁷⁸ Furthermore a plane-wave energy cutoff of 500 eV was used and found to produce excellent convergence. The three-dimensional Brillouin zone was sampled with a $12 \times 12 \times 12$ k -point Monkhorst-Pack mesh⁴⁴ for the cubic bulk (5 atom unit cell) and thin film structures and a $12 \times 12 \times 10$ k -point sampling mesh for the bulk orthorhombic structure (20 atom unit cell). For the orthorhombic films we used a $12 \times 12 \times 3$ k -point sampling. In all cases the tetrahedron method with Blöchl corrections⁴⁵ was used for the Brillouin zone integrations.

In the localized basis code SIESTA, the core and valence electrons were treated with norm-conserving fully separable⁴⁶ Troullier-Martin⁴⁷ pseudopotentials.⁷⁹ The localized atomic orbitals for each atom used a single- ζ basis set for the semicore states and a double- ζ for the valence states. Total energies were computed on a uniform real space grid with a cutoff of 800 Ry in order to reach comparable accuracy to the plane-wave code.⁸⁰ The Brillouin zone of the cubic structure was sampled with a $26 \times 26 \times 26$ k -point Monkhorst-Pack mesh, while the $Pbnm$ structure was sampled with a $15 \times 15 \times 12$ k -point mesh. Integrations were performed with a Gaussian broadening of 0.10 eV in all calculations.

The equilibrium lattice parameter for the cubic structure was found by fitting the total energy as a function of volume to the Murnaghan equation of state. Excellent agreement was found between the two codes (Table I), with a slight underestimate of the experimental lattice constant typical for the LSDA. The cell parameters and atomic positions of the orthorhombic structure (Table II) were optimized by starting from the positions reported in Ref. 28 and the ionic coordinates were relaxed until the Hellmann-Feynman forces on the atoms were less than $4 \text{ meV } \text{\AA}^{-1}$.

Investigations of the electronic structure of cubic SrRuO₃ have been described by several different groups^{22,28,32} within the LSDA; here we briefly summarize their conclusions and remark that our results are con-

	VASP	SIESTA
a/a_0	0.98	0.98
B (GPa)	200	219
B'	4.6	4.4
Moment ($\mu_B/\text{f.u.}$)	1.09	1.26

TABLE I: Results obtained for cubic SrRuO₃ within the local spin density approximation (LSDA) from the two codes used in this work. The equilibrium lattice constant relative to the experimental value ($a_0 = 3.9735 \text{ \AA}$) determined from high-temperature neutron diffraction data,⁴⁸ the bulk modulus B , the pressure derivative B' , and the magnetic moment per formula unit are given for each code. Very good agreement is found between the two codes. The notation for the codes are as follows, SIESTA: Spanish Initiative for Electronic Simulations with Thousands of Atoms local orbital code and VASP: Vienna Ab-initio Simulation Package plane-wave code.

Atom	Site	x	y	z
Sr	4c	-0.0050	0.03039	0.25
Ru	4a	0.5	0.0	0.0
O(1)	4c	0.0650	0.4942	0.25
O(2)	8d	0.7158	0.2834	0.0340

TABLE II: Calculated structural parameters for SrRuO₃ with the $Pbnm$ symmetry using VASP. Our calculated orthorhombic lattice constants are $a = 5.4924$, $b = 5.4887$, and $c = 7.7561 \text{ \AA}$.

sistent with the earlier calculations. A complete comparison of the electronic structure of cubic SrRuO₃ calculated with both VASP and SIESTA is made in Section IV. In all cases, a metallic ferromagnetic ground state is found to be stable, with strong Ru $4d$ character at the Fermi level. Substantial hybridization occurs between the O $2p$ states and the Ru $4d$ -states and no energy gaps are observed in the densities of states. The calculated magnetic moment is also always reduced from the fully ionic limit of $2 \mu_B$.

B. LSDA+ U

The first “beyond-LSDA” method that we use to treat the exchange and correlation (XC) within DFT is the local spin density approximation with Hubbard U (LSDA+ U).⁴⁹ Here we use the spherically averaged form of the rotationally invariant LSDA+ U introduced by Dudarev *et al.*,⁵⁰ in which only one effective Hubbard parameter, $U_{\text{eff}} = U - J$, is used, where U and J are the spherically averaged Hubbard repulsion and intra-atomic exchange for electrons with the angular momentum of interest; in this case Ru $4d$ states. We treat the double-counting term within the fully-localized-limit and note that this should more correctly describe the insulating side of the metal-insulator transition that we study

here; an improved description of the metallic side might be achieved using the recently introduced interpolation between the around-mean-field and fully-localized-limit extremes.⁵¹

Within these approximations, the LSDA+ U correction to the LSDA potential is

$$\Delta V(mm'\sigma) = -(U - J) \left(\rho_{mm'}^\sigma - \frac{1}{2} \delta_{mm'} \right) \quad , \quad (1)$$

where m, m' are the orbital indices, σ is the spin index, and $\rho_{mm'}^\sigma$ is the orbital occupation matrix. The effect of the LSDA+ U correction given by Eq. 1 is particularly transparent in the limit of diagonal $\rho_{mm'}^\sigma$ with orbital occupancies 1 or 0: Occupied orbitals experience a potential which is lower in energy by $(U - J)/2$ compared with the LSDA, and the potential for unoccupied orbitals is raised by the same amount.

In this study we varied U_{eff} from 0 to 6 eV for the Ru d -states, (the standard LSDA corresponds to a $U_{\text{eff}} = 0$ eV). Structural optimizations were also performed within LSDA+ U approximation, however negligible structural changes compared with the LSDA were observed.

C. Self Interaction Corrections

Our second approach for extending the treatment of the exchange and correlation is to correct for the spurious self-Coulomb and self-exchange interactions which arise within the LSDA, using the pseudopotential self-interaction corrected (pseudo-SIC) method.^{52,53,54} These self-interaction errors are small for materials with delocalized electronic states, but can be significant in systems with localized electrons where the interaction of an electron with itself is large.

Since the SIC in a periodic, extended system is not uniquely defined, many different methods have been proposed to remove SI in DFT calculations for solids (for a review see Ref. 55). The procedure followed in the pseudo-SIC method is to:

1. Project the occupied Bloch states onto the basis of the pseudo-atomic orbitals.
2. Correct the potential for each Bloch state by the SIC for the pseudo-atomic orbital weighted by the projection, and scaled to account for the relaxation energy.

Note that only the valence bands are corrected since the empty conduction bands, derived from orbitals where the occupation numbers are close to zero, are not self-interacting. This is in contrast to the LSDA+ U method, in which the occupied bands are lowered in energy and the unoccupied bands raised. In principle, however, the two formalisms would yield equivalent results if a suitable $U - J$ (corresponding to the SIC energy) were applied to all orbitals in the LSDA+ U calculation. Indeed,

whether the deficiencies of LSDA for strongly correlated systems derive from the absence of Hubbard U or the self-interaction error or both remains an open question. The pseudo-SIC method has some advantages over LSDA+ U , since it does not require a choice of which orbital to correct, nor of the U or J parameters, and it can be applied readily to both magnetic and non-magnetic systems. We note that this is the first application of pseudo-SIC to an itinerant-correlated system, so the comparison with our LSDA+ U results provides a test for the pseudo-SIC method.

IV. RESULTS & DISCUSSIONS

As we have mentioned, the electronic structure of SrRuO₃ has been investigated previously using the LSDA.^{22,28,32} Here we first revisit the LSDA with our own calculations, with an emphasis on understanding discrepancies between the experimental measured photoemission results^{18,19} and the calculated LSDA electronic structure of the orthorhombic material. We then extend our study to the two “beyond LSDA” approaches to examine correlation effects in *bulk Pbnm* and *Pm3m* SrRuO₃. Finally, we examine unsupported *films* of SrRuO₃ in both structures in order to analyse the nature of the experimentally observed metal-insulator phase transformation.

Cubic LSDA The total energies were calculated for both the ferromagnetically ordered and non-magnetic states of cubic SrRuO₃ using the optimized lattice parameters. With both electronic structure codes the ferromagnetic groundstate is always found to be lower in energy (VASP: 11.5 meV, SIESTA: 31.6 meV). Both codes yield very similar electronic structures. The density of states obtained using the VASP code is shown in Figure 2. The valence band is composed largely of O $2p$ states hybridized with Ru $4d$ states, with oxygen states predominately found in lower regions of the valence band and Ru states dominating at the Fermi energy. The large peak in the DOS near the Fermi level is caused by the fairly flat Ru t_{2g} bands near the Fermi level while the strongly hybridized e_g orbitals form broader bands at the bottom of the valence and conduction bands. The Sr $4d$ states are found around 5 eV above the Fermi energy.

The exchange splitting causes an energy shift between the majority spin and minority spin states; at the Γ -point a splitting of ≈ 0.50 eV is observed in the Ru $4d$ states, and of ≈ 0.20 eV in the O $2p$ states. The calculated magnetic moments per formula unit are found to be $1.09 \mu_B$ (VASP) and $1.26 \mu_B$ (SIESTA). With both implementations of DFT, approximately 70% of the moment is found on the Ru atoms, with the remaining distributed about the oxygen network. The slight enhancement of the magnetic moment calculated with SIESTA compared to VASP is due to SIESTA’s slight downward shift in energy of the Ru t_{2g} band relative to the Fermi energy. We note that the consistency between the two DFT fla-

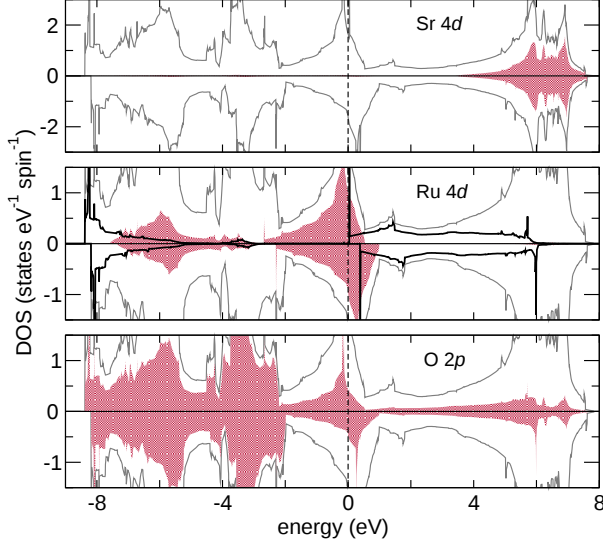


FIG. 2: (Color online) The total (gray line) and partial (shaded) spin-resolved densities of states for cubic SrRuO_3 calculated within the LSDA using VASP. (UPPER) Sr 4d states, (MIDDLE) Ru 4d states [the t_{2g} and e_g (unshaded, bold line) symmetries are shown], and (LOWER) O 2p states. The dashed line at 0 eV denotes the Fermi level.

vors is essential to our later discussion of the effect of electron-electron correlations in the electronic structure of SrRuO_3 , since the LSDA+ U approach has been implemented in the VASP code, and the pseudo-SIC method in the SIESTA code.

Orthorhombic LSDA Using the optimized LSDA lattice parameters for the $Pbnm$ structure, we find that the ferromagnetic ground state is 6.34 meV/f.u. lower in energy than the constrained paramagnetic structure, and additionally is 188 meV/f.u. (VASP) and 150 meV/f.u. (SIESTA) lower in energy than the ferromagnetic cubic phase. This energy stabilization can be associated with the oxygen octahedral tiltings and rotations, and agrees well with previous first-principles studies^{28,32} that used experimental lattice parameters⁵⁶ (the LSDA underestimates the lattice parameters by only about 1%). Also it is consistent with the experimental observation of ferromagnetic SrRuO_3 in the distorted GdFeO_3 structure.⁵⁶

The (P)DOS for the orthorhombic structure are shown in Fig. 3, and can be seen to be similar to those of the cubic structure discussed earlier (Fig. 2).⁸¹ Consistent with the reduction in Ru 4d – O 2p overlap resulting from the tiltings and rotations, the bandwidths are slightly narrower in the orthorhombic structure, with the t_{2g} bandwidth reduced by 0.35 eV, the e_g by 1.5 eV and the O 2p by 0.60 eV. This results in a pseudo-gap opening in the minority e_g bands at ≈ -2.2 eV and a 0.20 eV gap opening ≈ 0.80 eV above the Fermi level. Interestingly, the Ru 4d exchange splitting is reduced slightly to 0.30 eV at Γ . This is accompanied by a reduction in the magnetic moment compared with the cubic structure, to 0.79 μ_B /f.u. (VASP) or 0.92 μ_B /f.u. (SIESTA). As noted, the sponta-

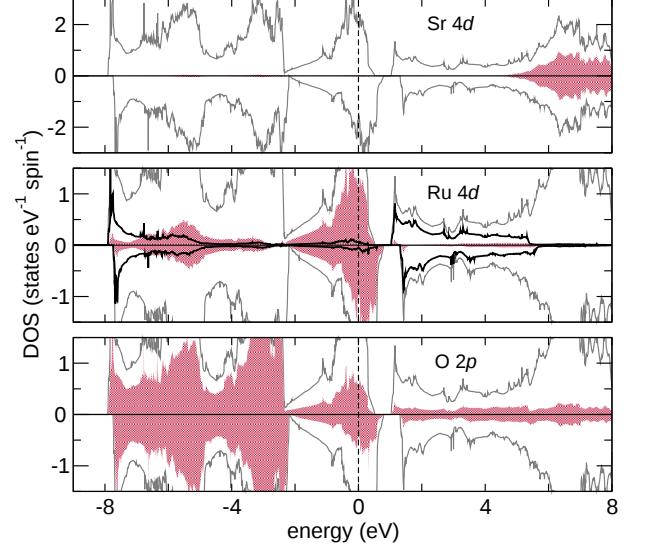


FIG. 3: (Color online) The total (grey line) and partial spin-resolved (shaded) densities of states for orthorhombic SrRuO_3 calculated within the LSDA using VASP. (UPPER) Sr 4d states, (MIDDLE) Ru 4d states [the t_{2g} and e_g (unshaded, bold line) symmetries are shown], and (LOWER) O 2p states.

neous magnetization in the bulk (films) has been reported to be near 1.6 μ_B (1.4 μ_B), the LSDA underestimate is likely the result of the usual LSDA overbinding leading to enhanced Ru 4d – O 2p covalency. Note that this underestimate as compared to experiment³¹ is significantly larger than that usually found for 3d transition metal oxides. It is further notable, because the orbital angular momentum is expected to be strongly quenched for 4d orbitals due to the cubic crystal field. We comment on the effect of including spin-orbit coupling later.

Finally for the LSDA section, we compare our first-principles LSDA results with recent photoemission spectroscopy (PES) data^{20,57,58} with the goal of identifying which features are driven by correlation. In an ideal single-electron picture, the measured PES would consist of narrow peaks corresponding to the energies required to excite non-interacting electrons from the valence band into the continuum. However, the photoemission energies are more accurately interpreted as differences between two many-body N -electron states: the ground state, and the excited state with a photoelectron and hole. The effect of the many-body interactions is to broaden the one-electron peaks and shift spectral weight into so-called quasiparticle peaks. The strongest reduction in spectral weight from correlation effects occurs from so-called coherent peaks near ϵ_F , and is accompanied by transfer of the spectral weight to higher energy features (incoherent peaks). Redistribution of the incoherent spectral weight into a well-defined satellite structure is indicative of strong correlations, whereas a redistribution into the background spectral distribution with a renormalization of the bandwidth indicates weak correlations.

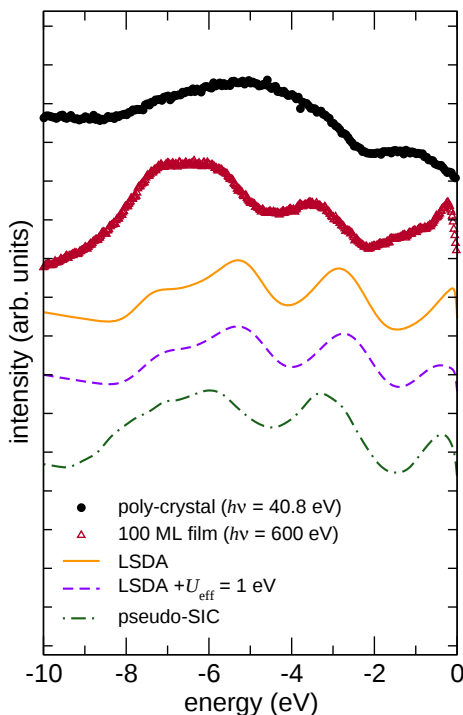


FIG. 4: (Color online) The experimental PES spectra for bulk polycrystalline⁵⁹ SrRuO₃ (filled circles) and 100 monolayer SRO film⁶⁰ (triangles) grown on SrTiO₃ are compared to the calculated LSDA(+ U) and pseudo-SIC densities of states. The calculated DOS are broadened with an energy dependent Lorentzian (FWHM = $0.1|\epsilon - \epsilon_F|$ eV) and a Gaussian function (0.34 eV FWHM). An energy dependent parabolic background has also been added.

In Figure 4, we show two experimentally measured spectra (see Refs. 18 and 59 for further information on the sample preparation) and our calculated LSDA results. First we comment on the discrepancies between the bulk polycrystalline spectrum and that of the thin film. Comparing the experimental spectra, we see that the thin film at 100 monolayers (which is representative of the bulk material) shows stronger coherent peaks than the highly broadened structure of the polycrystalline sample. In both cases however, the spectra are dominated by three principle features from the Ru t_{2g} states near the Fermi level and the O $2p$ states between -8 and -2 eV. If we look more closely around the Fermi level, the polycrystal sample has substantially reduced spectral weight, whereas near -1.3 eV it is enhanced compared to the film. This shift in the spectral weight to the incoherent peak agrees well with previous experimental comparisons⁶¹ made between SrRuO₃ films and polycrystals and is attributed to the creation of near surface states induced during *in situ* scraping and not due to intrinsic correlation effects. Additionally the presence of grain boundaries and compositional defects are also known to yield reduced coherent peak features in polycrystalline samples. For the remainder of this study, we therefore restrict our comparison of

the PES data to the 100 monolayer film, since it more accurately describes the intrinsic electronic structure.

By comparing to our calculated densities of states, we can assign the peak features in the PES data to the corresponding electronic states. In order to make the comparison with our calculated DOS, we convolute an energy dependent Lorentzian function [full width at half maximum (FWHM) = $0.1|\epsilon - \epsilon_F|$ eV] with the calculated DOS to account for lifetime broadening. A Gaussian function with a FWHM = 0.34 eV is also used to account for the instrumental resolution, and an energy dependent parabolic background is also added. We find that the bands between approximately -2.5 eV and -8 eV are due to the O $2p$ states, with the peak of the non-bonding state centered at -3 eV. In the range between -8 eV up to the Fermi level are the occupied Ru $4d$ states, with the t_{2g} state lying across the Fermi energy beginning at -3 eV.

Some important discrepancies exist between our LSDA results and the spectroscopic data: The Sr $4d$ states are positioned approximately 1.5 eV lower in energy than is expected from the experimental spectra as determined in the BIS and XAS spectra (not shown).^{20,57} The spread of the O $2p$ states is also underestimated by 2 eV. The most drastic difference, and one examined many times in the literature, occurs in the Ru $4d$ states, where indications of correlations are found. From Fig. 4 it is clear that the t_{2g} states at ϵ_F are overemphasized in the LSDA calculation. Experimentally the Ru $4d$ spectrum shows only a small weak coherent peak and is 1.5 eV broader than the LSDA predicts. As mentioned, the signature of strong correlations as observed in the PES data is the strong renormalization (or even absence) of the quasi-particle peak near ϵ_F or large satellite peaks. The large coherent t_{2g} peak about 0.5 eV below the Fermi level has a substantial incoherent feature near 1.3 eV and is good evidence for localized electronic states from strong correlation effects. We also note that Santi and Jarlborg³⁴ suggest that this suppression of the t_{2g} states is possibly due to small matrix elements for the $d \rightarrow f$ and $d \rightarrow p$ transitions. Using our two “beyond-LSDA” techniques to introduce correlation effects, we attempt to address whether this incoherent feature, not found in the LSDA calculations, is indeed due to strong electron-electron interactions.

More recent ultraviolet photoemission spectroscopy (UPS) data²¹ suggests that the Ru stoichiometry plays a significant role in determining the spectral weight and intensity of the t_{2g} peak at the Fermi level. For stoichiometric SrRuO₃ films, the spectral intensity near the Fermi level is in much better agreement with the calculated PDOS, while Ru deficient samples have a reduced intensity. These facts suggest that previous comparisons may have been made with non-stoichiometric Ru samples, which may be caused by a high partial pressure of oxygen during growth. Although the Ru cation deficiency appears to explain the discrepancy with experimentally measured spectra, it is difficult to fully remove correla-

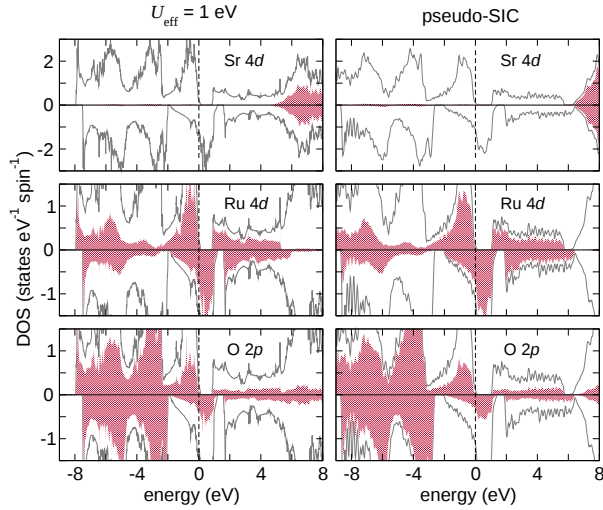


FIG. 5: (Color online) The total (grey line) and partial spin-resolved (shaded) density of states for orthorhombic SrRuO₃ calculated with $U_{\text{eff}} = 1$ eV (left) and pseudo-SIC (right) are shown in each panel. (UPPER) Sr 4d states, (MIDDLE) Ru 4d states and (LOWER) O 2p states.

tion effects that implicitly result from changes in stoichiometry, e.g. the *d* bandwidth can be varied by changing the volume of the unit cell via changes in O–Ru–O bond angles which occurs upon Ru vacancy formation. For example, Siemons and co-workers found the enhancement of an incoherent peak at approximately 1.5 eV below the Fermi level in ruthenium poor samples measured with ultraviolet photoemission spectroscopy.²¹ Future first-principles calculations may be able to identify the role of these defects.

It is clear that the LSDA poorly describes the electronic and magnetic structure of bulk SrRuO₃, and this suggests that some underlying physics is missing in the local spin density approximation. We next explore two extensions of that description to include electron-electron correlation effects.

A. “Beyond LSDA”

We now explicitly add correlation effects into our electronic structure calculations for SrRuO₃ using the two methods outlined above. The pseudo-SIC and LSDA+*U* methods give very similar results when a $U_{\text{eff}} = 1.0$ eV is used. Therefore we first compare the correlated and LSDA results, and later point out the small differences between results from the two correlated formalisms.

Orthorhombic Figure 5 shows the densities of states calculated with LSDA+*U* with a $U_{\text{eff}} = 1.0$ eV and the pseudo-SIC method for *Pbnm* SrRuO₃. Compared with the LSDA, the correlated bands are narrower, with energy gaps appearing in both spin channels. The inclusion of correlations causes a 70% drop in the total DOS at the Fermi level compared with LSDA, with the result that the

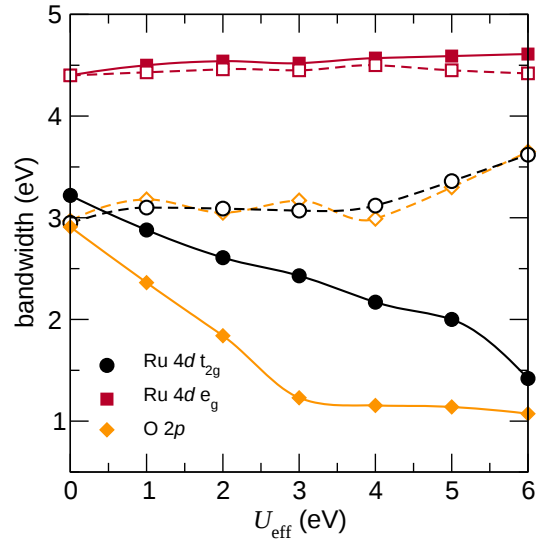


FIG. 6: (Color online) The orbital bandwidth dependence on U_{eff} for orthorhombic SrRuO₃. The minority spin states are shown by the unshaded symbols and the lines are a guide to the eye. Using the pseudo-SIC method, the majority (minority) bandwidths are slightly larger than with the LSDA+*U* method, but the relative ratios are consistent: Ru 4d $t_{2g} = 3.30$ (3.50) eV, Ru 4d $e_g = 4.75$ (4.60) eV, and O 2p = 3.25 (3.50) eV.

contribution to the Ru 4d states is almost entirely derived from the minority spin channel, and the material is close to half-metallicity. This significantly enhances the magnetic properties compared to the LSDA, increasing the magnetic moment per formula unit to around $1.0 \mu_B$, and enhancing the exchange splitting of the Ru 4d states at Γ to 0.45 eV (≈ 0.30 eV in LSDA). In addition, the peak positions of the correlation-included densities of states are in better agreement with the experimental spectra (Fig. 4), although the intensity of the O 2p peak at ≈ -7 eV is still too low compared with that of the Ru t_{2g} peak.

The main difference between the electronic structures calculated with $U_{\text{eff}} = 1$ eV and the pseudo-SIC methods is a larger bandwidth of the occupied orbitals, by ≈ 1.7 eV, in the pseudo-SIC calculation. This has the greatest effect on the Ru 4d bands and the oxygen 2p bands near -8.0 eV. As a result, the pseudo-SIC shows better agreement with the PES in the bandwidth for the O 2p states between -8 and -4 eV, and the t_{2g} states at the Fermi level have been more accurately suppressed.

In order to understand how the hybridization changes as electron-electron correlation effects are included, we plot in Figure 6 the change in bandwidth for the Ru 4d and O 2p states as a function of U_{eff} for orthorhombic SrRuO₃. As the amount of correlation is increased in the calculation through the U_{eff} term, the majority Ru t_{2g} and O 2p bandwidths are strongly reduced, and upon narrowing (both by approximately 1.80 eV) half-metallic behavior is observed for $U_{\text{eff}} > 2$ eV. On the other hand,

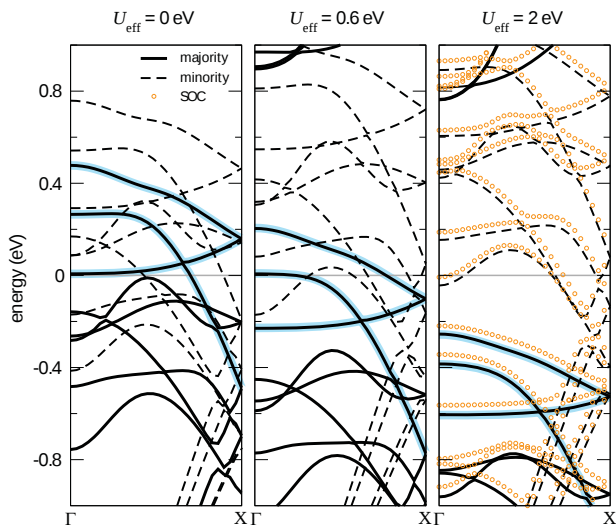


FIG. 7: (Color online) LSDA+ U band structures along $\Gamma-X$ calculated with VASP for ferromagnetic orthorhombic SrRuO₃. The horizontal grey line marks the Fermi level. Majority (minority) bands are shown as the bold (dashed) lines. The highlighted bands indicate the filling of the majority t_{2g} hole pocket, which gives rise to the observed half-metallicity at large Hubbard U values. For $U_{\text{eff}} = 2$ eV, the open circles show the results of calculations including spin-orbit coupling.

only a weak dependence in the orbital bandwidth is observed for the minority spin states. The valence bandwidth never narrows sufficiently in the bulk material (due mostly to the insensitivity of the minority t_{2g} bands to correlation effect) to open an insulating gap in both spin channels.

Since the half-metallic ground state that we find for $U_{\text{eff}} > 2$ eV is not observed experimentally, and motivated also by the observation of large magnetic anisotropy in Kerr rotation measurements⁶² on SrRuO₃ we have repeated our calculations with spin-orbit coupling (SOC) effects included. In Figure 7 we plot the band structure along $\Gamma-X$ in the Brillouin zone as a function of increasing U_{eff} . We see that the t_{2g} bands move down in energy with increasing U_{eff} , forming a small hole pocket which becomes completely filled at $U_{\text{eff}} = 2$ eV giving the half-metallic behavior. We note that without careful sampling of the Brillouin zone, this hole pocket is often missed, and half-metallic behavior can be prematurely predicted. Furthermore, we superimpose the band structure calculated with $U_{\text{eff}} = 2$ eV and spin-orbit coupling in Figure 7. We find here that the degeneracy of the t_{2g} bands is completely removed, and the highest occupied majority band is pushed only 0.05 eV higher in energy. Furthermore, this splitting decreases at larger U_{eff} values. These results indicate that the inclusion of spin-orbit coupling does not have a large effect on the band structure. Although spin is strictly not a good quantum number, due to quenching of the angular momentum by the crystal field, the total angular momentum is well-approximated by the spin only component, and therefore

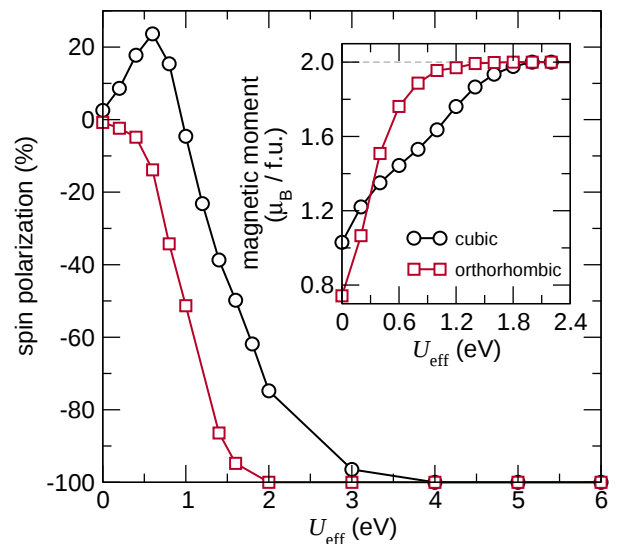


FIG. 8: (Color online) Calculated spin polarization at the Fermi level (P_0^{EF}) for orthorhombic and cubic SrRuO₃ calculated with VASP as a function of U_{eff} . The pseudo-SIC calculations give a spin polarization of +2.0% and 8.8% for each structure, respectively. (INSET) Calculated magnetic moment per formula unit for each structure type with LSDA+ U . The pseudo-SIC calculations yield a magnetic moment of 1.99 and 1.77 μ_B /f.u. for each structure, respectively.

the calculated proximity to half-metallicity in SrRuO₃ is robust to spin-orbit coupling effects.

Finally we investigate the enhancement of the magnetic properties as U_{eff} is increased. In Figure 8 (inset) we show the magnetic moment per formula unit as a function of increased correlation for both crystal structures of SrRuO₃. For example, the magnetic moment per Ru atom is found to be 1.97 μ_B with $U_{\text{eff}} = 1.0$ eV and 1.99 μ_B with the pseudo-SIC. At $U_{\text{eff}} \geq 2$ eV saturation of the moment occurs, and the localized ionic moment is observed (2.0 μ_B).

Cubic We complete this discussion by describing the differences in the bulk cubic electronic structure with correlation effects added in order to isolate the contribution of the octahedral distortions in the orthorhombic structure to the bandwidth narrowing. This analysis will provide the framework for exploring the MI-transition in the SrRuO₃ thin films. Overall the weight and shape of the total density of states with correlations included is consistent with that calculated in the LSDA, with the exception that the large densities of states at the Fermi level (majority t_{2g} states) are pushed lower in energy. As was observed in the orthorhombic structure, a similar DOS is found between both correlation methods, and in general the occupied orbitals with the pseudo-SIC are broadened by 1.5 eV in energy compared to those calculated with the LSDA+ U . As in the orthorhombic structure the minority bandwidths in the cubic case are insensitive to the choice of U_{eff} while the majority O $2p$ and Ru t_{2g} bandwidths narrow considerably (1.2 and 1.8 eV,

respectively). Furthermore, the observed exchange splittings for the various states are overall larger for the cubic structure, and this is consistent with the electronic structures calculated with the LSDA. The calculated magnetic moment for $U_{\text{eff}} = 1$ eV is $1.64 \mu_B$ and agrees well with that from the pseudo-SIC method ($1.77 \mu_B$). Again, for values of $U_{\text{eff}} > 2$ eV a half-metallic ground state becomes stable while with the pseudo-SIC a fully metallic ground state is always maintained.

To summarize the bulk SrRuO_3 results, each of the two “beyond LSDA” methods described here improve the description of the electronic and magnetic structure. However the precise experimental spectra are not fully reproduced although correct peak assignments can be made. The addition of a small Hubbard term $U_{\text{eff}} = 0.6$ (1.2) eV for the orthorhombic (cubic) structure, or alternatively by correcting the SI error in LSDA, also improves the Ru t_{2g} bandwidths with respect to experiment.²⁶ The total width of the O $2p$ band structure is also increased to approximately 7 eV in agreement with the spectral weights. We therefore suggest that SrRuO_3 can best be described as *weakly strongly-correlated*. Finally, as stated earlier, the intensity at ϵ_F has been decreased in comparison to LSDA, although it is still larger than experimentally observed.

B. Spin Polarization & Transport Properties

SrRuO_3 has been experimentally reported⁶³ to belong to the class of negatively spin-polarized materials—characterized by a greater number of *minority* spins at the Fermi surface which are aligned anti-parallel to the bulk magnetization. However, the magnitude of the spin polarization at the Fermi level remains controversial within the experimental community, due in part to the different definitions of the spin polarization (resulting from the different experimental techniques used to probe this quantity), as well as to difficulties in performing the experiments. Furthermore, the theoretical community has also not converged on the magnitude of the spin polarization, due to the sensitivity of the Ru t_{2g} states near ϵ_F on the choice of exchange-correlation functional. In this section, we perform first-principles transport calculations on orthorhombic and cubic SrRuO_3 , and compare our results to the available data in the literature. We also describe the various definitions of the spin polarization commonly used in the literature, and relate them to calculated *ab initio* quantities.

The spin polarization at the Fermi level $P_0^{\epsilon_F}$ can be calculated from the density of states at the Fermi level (N_{ϵ_F}) by the following ratio,

$$P_0^{\epsilon_F} = \frac{N_{\epsilon_F}^{\uparrow} - N_{\epsilon_F}^{\downarrow}}{N_{\epsilon_F}^{\uparrow} + N_{\epsilon_F}^{\downarrow}}. \quad (2)$$

Using this definition with the LSDA, the sign of the spin polarization for orthorhombic SrRuO_3 is ambiguous: We

find that with the planewave code $P_0^{\epsilon_F} = -2.95\%$ while the local orbital code gives a positive spin polarization of 2.00%. In contrast, for the cubic structure we find a positive spin-polarization ($P_0^{\epsilon_F}$) in both first-principles calculations, +1.3% (VASP) and +8.8% (SIESTA). The reason for this discrepancy is the sensitivity of the exchange splitting of the Ru $4d$ bands near the Fermi level to the structure. The majority t_{2g} band is positioned very close to the band edge, and its precise location is sensitive to the finer details of the DFT calculation. As a result, the large spread in the calculated spin polarization is not surprising, and since the magnitudes of the spin polarizations are small, changes of a few percent can give a change of sign.

When correlations are introduced, $P_0^{\epsilon_F}$ increases in magnitude significantly and is negative in all cases. The spin polarization as a function of U_{eff} for the orthorhombic and cubic structures is plotted in Figure 8. The spin-polarization calculated for the orthorhombic structure with the pseudo-SIC method is -85.7%, compared with a value of +2.00% when the SI error is not corrected. This value agrees with that obtained by the LSDA+ U when $U_{\text{eff}}=1.4$ eV. We previously found that smaller U_{eff} values optimize the agreement between pseudo-SIC and LSDA+ U band structures and magnetic properties, suggesting that the pseudo-SIC transport results should be regarded as providing an upper bound on the magnitudes of spin-polarization. For U_{eff} exceeding a critical value of 1.6 eV (3.0 eV) the half-metallic groundstate becomes the most stable solution for orthorhombic (cubic) structure, as an energy gap opens in the majority t_{2g} band and $P_0^{\epsilon_F}$ reaches 100%.

Despite being the most natural definition of spin polarization at the Fermi level, determining $P_0^{\epsilon_F}$ as defined in Eq. 2, is a non-trivial experimental process, since the spectroscopic measurements required typically have poor energy resolution. As knowledge of the degree of spin polarization in a ferromagnet is crucial for its use in spintronics, several different experimental methods have been developed in order to determine this quantity.

The *transport* spin polarization can be defined as

$$P = \frac{I^{\uparrow} - I^{\downarrow}}{I^{\uparrow} + I^{\downarrow}}, \quad (3)$$

where I^{σ} is the spin dependent current. However I^{σ} is not directly observable and must be determined indirectly. The transport spin polarization now depends on the experiment in question, and in particular whether the transport is in the ballistic or diffusive regime. In the ballistic limit the current is proportional to $N_{\epsilon_F} \nu_F$, while for diffusive transport it is proportional to $N_{\epsilon_F} \nu_F^2$ (assuming both spin species have the same relaxation time), where ν_F^{σ} are the spin dependent Fermi velocities.

Therefore the transport spin polarization at the Fermi level can be redefined as

$$P_n^{\epsilon_F} = \frac{N_{\epsilon_F}^{\uparrow} \nu_F^{\uparrow} - N_{\epsilon_F}^{\downarrow} \nu_F^{\downarrow}}{N_{\epsilon_F}^{\uparrow} \nu_F^{\uparrow} + N_{\epsilon_F}^{\downarrow} \nu_F^{\downarrow}} \quad (4)$$

	Orthorhombic	Cubic
	$P_n^{\epsilon_F}$ % (LSDA, pseudo-SIC)	
$n = 0$	+2.00, -85.7	+8.80, -16.1
$n = 1$	-1.44, -92.9	-8.99, -50.9
$n = 2$	-15.1, -98.0	-32.9, -79.5

TABLE III: Transport spin polarizations calculated with SMEAGOL, according to the definition of Eq. 4 using both the LSDA and pseudo-SIC. Results for both the orthorhombic and cubic SrRuO₃ structures are included.

where $n = 1$ for ballistic transport or $n = 2$ for diffusive transport^{64,65}. If $n = 0$, this definition reduces to that of the spectroscopic polarization, $P_0^{\epsilon_F}$.

An additional definition of polarization is used in Meservey-Tedrow style tunneling experiments. Here the spin dependent DOS are weighted by their corresponding tunneling matrix elements. Such an experiment has been performed for SRO and report approximately a -10% spin polarization.⁶³ Inverse tunnel magnetoresistance measurements also agree that SRO is negatively spin polarized.² This is in agreement with the majority of the calculations which find that SRO is a negatively spin polarized material at the Fermi surface.

The point-contact Andreev reflection (PCAR) technique, which is based on the process of Andreev reflection,⁶⁶ and developed as an experimental method in the work of Soulen *et al.*⁶⁷ and Upadhyay *et al.*,⁶⁸ has been used successfully to determine the magnitude of the transport spin polarization, although it is not sensitive to its sign. Experimental results^{69,70,71} using this method report values ranging between 51% and 60%. It should be noted that in the Andreev experiment the polarization is not uniquely defined, in that it must be extracted from the data through a fitting procedure and involve terms that describe the transmittivity of the interface between the ferromagnet and the superconductor. These parameters are typically difficult to determine precisely and consequently introduce further uncertainty in the experimental spin polarization. Furthermore, it is important to note that in all PCAR experiments, it is necessary to establish whether the transport is in the ballistic, diffusive or intermediate regime (non-integer n) which ultimately depends on the transmittivity of the interface. The experimental results for SRO are further complicated by the fact that the transport in the system has been measured in both regimes.

To allow for a direct comparison with the PCAR experiments, the transport spin polarization in both the ballistic and diffusive limit was determined using the *ab initio* electronic transport code SMEAGOL.⁷² Here we calculated the transport at zero bias through both the orthorhombic and cubic structures,⁸² and present the results in Table III and Figure 9. The shortcomings of the LSDA in describing the spin polarization at the Fermi level in SrRuO₃ are again apparent. The highest spin polariza-

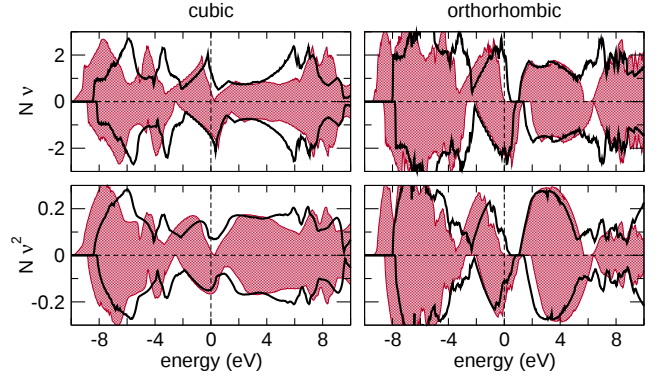


FIG. 9: (Color online) Spin dependent transport coefficients, $N\nu$ and $N\nu^2$, calculated with both the LSDA (unshaded) and pseudo-SIC (shaded).

tion obtained with the LSDA for the orthorhombic structure is -15% and it is obtained in the diffusive limit. This is notably smaller than the experimental PCAR results measuring the same quantity, $P_2^{\epsilon_F}$. As shown in Fig. 9, on changing from $P_0^{\epsilon_F}$ to $P_2^{\epsilon_F}$ the polarization increases and becomes more negative. Since the group velocity tends to zero at the band edge, and is often maximized at the band center, higher powers of n in $P_n^{\epsilon_F}$ suppress the contribution of the Ru 4d states at the band edge while enhancing those at the band center. From Figure 9 it is then clear that the large negative polarization is a consequence of the center of the *majority* Ru 4d band positioned approximately 1 eV below the Fermi level, while the *minority* Ru 4d band center is aligned across the Fermi level.

Further enhancement is seen by introducing correlation; for example, by correcting for the SI error, the spin polarization increases due to the reduction of the number of majority Ru t_{2g} states at the Fermi level. The correlated *ab initio* calculations now give very high spin polarization, ranging between -85.7% and -98.0% where as the highest value achieved experimentally is just 60%. Qualitatively similar results are found for the cubic structure, although the SIC in general has a smaller influence on the spin polarization. For example, $P_1^{\epsilon_F}$ goes from -8.99% (LSDA) to -50.9% (pseudo-SIC), while $P_2^{\epsilon_F}$ goes from -32.9% to -79.5%.

It is also useful to note the strong dependence of spin polarization on distance from the Fermi level. In Figure 10 we show for the orthorhombic structure that if the Fermi level is moved just 100 meV into the valence band, $P_1^{\epsilon_F}$ is decreased to -81.4%, while moving E_F by -200 meV decreases it further to -59.8%, bringing it within the experimental range of values. In practice this shift in the Fermi level can be realized by off-stoichiometric compounds such as those investigated by Siemons *et al.*²¹

The discrepancy between the computational and experimental results could be then due to a number of factors: For example, there are several known limitations with PCAR including spin-flip scattering events which could drastically reduce the measured value of P^{ϵ_F} , as

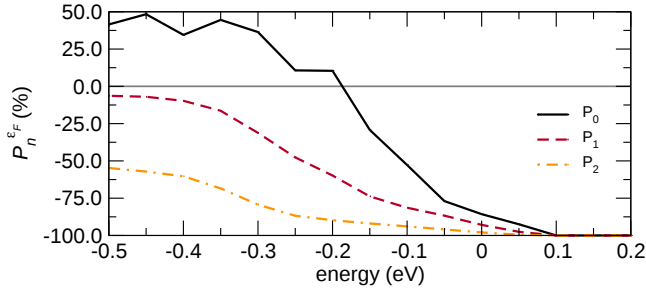


FIG. 10: (Color online) Spin polarization defined according to Eq. 4 as a function of distance from the Fermi energy (set to 0 eV) and calculated with the pseudo-SIC for the orthorhombic structure.

well as the possible ambiguous fit of PCAR measurements to a multiparameter model.⁷³ We also note that spin-orbit coupling, which we did not account for in our transport calculations, could reduce the spin polarization at the Fermi level.

Despite these disparities, both *ab initio* calculations and experiment show SrRuO₃ with a high negative spin polarization. As expected, LSDA underestimates the spin polarization at the Fermi level, whereas the inclusion of correlation through the correction of the SI error with the pseudo-SIC results in much better agreement between theory and experiment.

C. Thin films

The electronic and magnetic structure of epitaxially grown oxide multilayers can be tuned by controlling the film thickness. In particular, it has been demonstrated that metallic SrRuO₃ can be transformed into an insulating state by growing films thinner than five monolayers on SrTiO₃ substrates.¹⁸ It was also found that the Curie temperature decreases with reduced film thickness, along with the disappearance of strong ferromagnetic order. Photoemission experiments show a shift in the spectral weight to the incoherent peak features in the spectra, suggesting that these effects are a result of changes in electron-electron correlation effects. With our first-principles techniques, we systematically investigate whether we can reproduce this transition purely from structural confinement, or by also including correlation effects and/or the octahedral tiltings of the orthorhombic structure. For the remainder of this section, we choose to include correlation with the LSDA+*U* method, rather than the pseudo-SIC method, and note that from the discussion so far, both methods reproduce similar electronic structures.

Cubic LSDA slabs To investigate the effects of structural confinement on the metal-insulator transition, we first performed a series of slab calculations (from 1 to 5 unit cells thick) on cubic SrRuO₃ constrained to the calculated bulk equilibrium SrTiO₃ lattice parameter. This

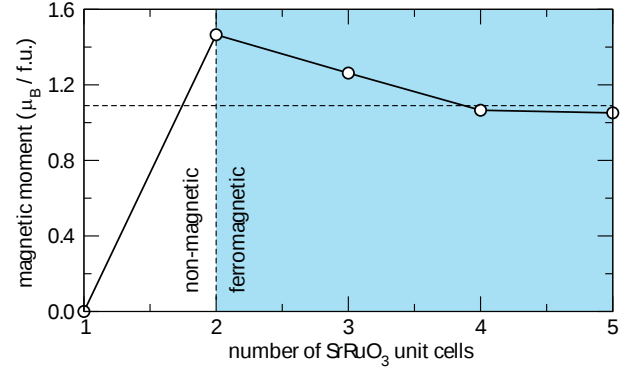


FIG. 11: (Color online) Magnetic moment dependence on slab thickness for cubic SrRuO₃. The bulk LSDA magnetic moment is shown as the dashed line. The total energy differences are calculated for the spin-polarized films with respect to the non-magnetic ground state.

is in part motivated by the fact that good epitaxy is made with the substrate surface, and that tilting of the octahedra may be suppressed. Additionally, it is computationally more feasible to systematically investigate these smaller supercell slabs. We discuss later the effect of including the octahedra tiltings in the orthorhombic thin films; we saw earlier that this structural effect is important in fully describing the subtle details of the electronic structure of SRO. In all calculations the slabs were terminated with a SrO surface, to be consistent with that experimentally observed to be the most thermodynamically stable.⁷⁴

In Figure 11 we plot the Ru magnetic moment (per f.u.) as a function of increasing slab thickness. We find that the LSDA films become non-magnetic below a critical thickness of only two monolayers; this is lower than the experimentally observed loss of the strong ferromagnetic order below six monolayers.⁷⁵ In addition, all of our calculations on the cubic films remain metallic down to one monolayer. Experimentally the situation is different and insulating behavior is observed in heteroepitaxial thin films at six monolayers on SrTiO₃. At one unit cell, where all atoms are surface-like, the magnetic moment is considerably suppressed from its bulk value, and the non-magnetic structure is actually lower in energy. An enhancement in the magnetic moment is observed at two unit cells in thickness; the moment then decreases toward the bulk value as the film thickness grows. For films larger than two unit cells, the ferromagnetic ground state is always found to be stable. In a mean field theory approach, the energy difference between the ferromagnetic and the paramagnetic ground states Δ can be expected to be proportional to the Curie temperature T_c according to $k_B T_c = \frac{2}{3} \Delta$. For the four and five unit cell slabs, we find mean field T_c 's of 170 and 120 K, respectively; these values are close to the experimental bulk value of 160 K suggesting that even in these thin films the strong itinerancy remains. This is consistent with

temperature dependent magnetization data recorded on strained and free standing films⁷⁶ as well as on ultra-thin SrRuO₃ films.⁷⁵ Additionally, the spin-polarization $P_0^{\epsilon_F}$ as a function of slab thickness (not shown) exhibits a large negative polarization at two unit cells, while a small positive spin-polarization is found with increasing thickness (consistent with our bulk spin polarization calculations). Most importantly, the insulating state is not found in any of the cubic slab calculations nor is the non-magnetic ground state generally favored (the one unit cell case is an exception and is due to competing interactions from surface effects).

To better understand how the magnetism is distributed in the slabs, we have also calculated the layer-by-layer local density of states (LDOS). As in the bulk case, on average the majority of the spin ($\approx 65\%$) is located on the Ru atom, with the remaining found on the oxygen network. Interestingly, the Ru atoms closest to the surface layers experience a suppressed magnetic moment for each slab. This is in contrast to most transition metal (non-oxide) ferromagnets, where often enhancement occurs due to a loss of coordination, weaker interatomic hybridization, and enhancement of the orbital angular momentum. In this oxide, enhanced covalency at the surface layer may be responsible for the reduced magnetism.

Before adding correlation effects in the cubic slabs, we first discuss the changes in the electronic structure due to the thin film geometry. The overall shape and weight of the density of states for the cubic slab and the bulk cubic LSDA calculation are very similar suggesting that confinement effects are minimal. The calculated exchange splittings are also similar with the exception that the Ru 4d states are split by approximately 0.25 eV. A small gap in the minority e_g states opens at approximately -4.30 eV, and partial occupation of the majority e_g states occurs; these features are not observed in the bulk cubic LSDA calculation. For a free standing, three unit cell film we find that the structure has a magnetic moment of 1.26 μ_B and a spin polarization of +13.2% within the LSDA, both larger than the bulk cubic values of 1.09 μ_B and +1.3% respectively. The increased positive spin polarization is a result of the band center of the minority Ru 4d states shifting to higher energy in the thin films. To summarize the results for the cubic SrRuO₃ thin films, we do not find a metal-insulator transition as a function of film thickness, although we do find a slightly enhanced magnetization. We therefore are able to rule out the effect of dimensional confinement as the driving force for a metal-insulator transition.

Cubic LSDA+U slabs We now examine the effect of adding correlation in the calculations for the cubic thin films in order to determine if electron-electron correlation in these structures is sufficient to obtain a metal-insulator transition. Here we use a $U_{\text{eff}} = 2$ eV, which although larger than that we described earlier to more accurately reproduce the PES spectra, does allow us to verify that in the absence of insulating behavior, the driving force for the MI-transition is not due to intrinsic correlation

effects. Although the numbers we discuss here are particular to a three unit cell thin film we note that the general trends are consistent across the series of cubic thin films. In contrast to the LSDA calculations, when a finite Hubbard U is placed on the Ru 4d states, we find that the majority e_g states are completely unoccupied, and occupation of the majority O 2p states near -2.3 eV is enhanced over the minority O 2p states which nearly open a gap in the minority spin channel. An enhancement in the exchange splitting for the Ru d orbitals is also observed with $U_{\text{eff}} = 2$ eV compared to $U_{\text{eff}} = 0$ eV, while the valence bandwidth is reduced. For the cubic slab with $U_{\text{eff}} = 2$ eV, the narrowing of the bandwidth nearly stabilizes a half-metallic ground state, as the majority Ru t_{2g} bands become completely filled. Despite these small changes in the occupation of the Ru 4d levels, we do not find an insulating ground state in any of the cubic slabs even in the presence of strong correlations ($U_{\text{eff}} < 6$ eV). Regarding the magnetic moment in these slabs, we find 2.0 $\mu_B/\text{f.u.}$ for $U_{\text{eff}} = 2$ eV, and a corresponding spin polarization at the Fermi level of -85.9%. These results are consistent with the effects of adding correlation in bulk cubic SrRuO₃, and because an insulating ground state is not achieved, we suggest that neither correlations nor structural confinement (from our previous discussion) are sufficient to induce a metal-insulator transition.

Orthorhombic LSDA slabs We now address films of orthorhombic SrRuO₃ which allow the full octahedral distortions found in the bulk experimental structure to occur. Earlier we showed that the effect of these distortions in the bulk is to reduce the t_{2g} valence bandwidth; in this section we examine whether these distortions with the addition of a confined geometry in a thin film form can stabilize the experimentally observed insulating SrRuO₃ ground state. With the relaxed coordinates for bulk *Pbnm* SrRuO₃, we calculate the electronic ground state for a three unit cell thick slab separated by 10 Å of vacuum on each side and SrO termination layers within both the LSDA and LSDA+ U method ($U_{\text{eff}} = 2$ eV).⁸³

We now discuss the changes in the electronic structure of the orthorhombic thin film: In Figure 12 we show the (P)DOS for the three unit cell slab with and without correlation. With the LSDA in the thin film system, the exchange splittings are similar to the bulk LSDA orthorhombic calculations, and the character around the Fermi level remains a mixture of majority and minority Ru t_{2g} . Energy gaps similar to those found in the bulk are observed in other regions of the electronic structure with the exception that an additional gap opens in the minority t_{2g} states at -2.5 eV, which is not observed in the bulk calculation.

We now compare the magnetic properties of the LSDA slab calculation to the bulk *Pbnm* LSDA calculation. With the LSDA method, we find a magnetic moment of 1.01 μ_B per Ru atom and a spin polarization at the Fermi level of $P_0^{\epsilon_F} = -7.96\%$ (compared to a bulk orthorhombic structure where a moment of 0.79 μ_B , and spin-

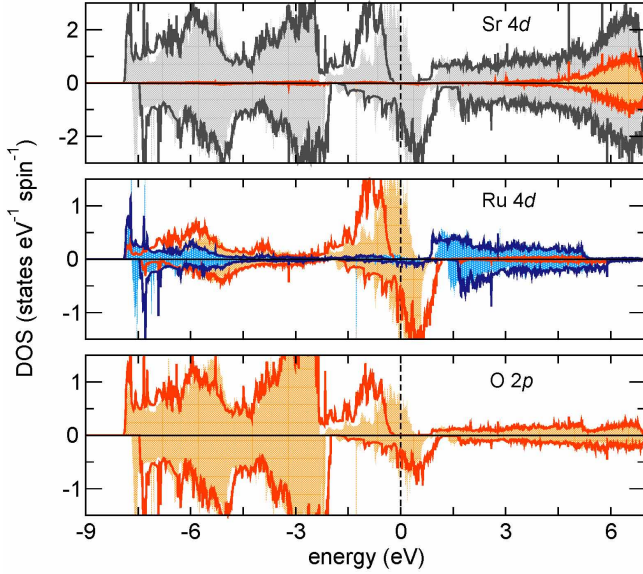


FIG. 12: The total and partial spin-resolved density of states for a three unit cell orthorhombic SrRuO_3 slab calculated with $U_{\text{eff}} = 0$ eV (shaded) and $U_{\text{eff}} = 2$ eV (unshaded, bold) are shown in each panel. (UPPER) Total (grey) and Sr $4d$ -states, (MIDDLE) Ru $4d$ -states, t_{2g} and e_g , and (LOWER) O $2p$ -states.

polarization of -2.95%). Therefore, we find enhanced magnetic properties in the thin film geometry when the octahedral tiltings are included. However we still do not find an insulating ground state.

Orthorhombic LSDA+ U slabs Finally we incorporate correlation into the orthorhombic slab calculations and examine the effect on the electronic and magnetic structure. We have already demonstrated that a $U_{\text{eff}} = 2$ eV is sufficient to establish a half-metallic ground state in the bulk orthorhombic structure; therefore, we use this limit to establish whether correlation can drive the insulating ground state. If we do not find a metal-insulator transition even at this large Hubbard U value, we can be certain that the effect is not due to correlation. In general, the shape and weight of the densities of states and exchange splittings for the different states remains similar to the orthorhombic LSDA slab calculation, however unlike the cubic slabs, the valence bandwidth does not noticeably narrow.

With the addition of the Hubbard U term in the calculation, the half-metallic ground state becomes stable, with 0.70 eV energy gap opening in the majority spin states. This behavior is realized by the minority t_{2g} bands shifting higher in energy while the majority bands become completely occupied. The majority e_g band is also lowered in energy from 1.0 eV in the LSDA slab calculation ($U_{\text{eff}} = 0$ eV) to 0.50 eV, while the minority spin-states move 0.30 eV higher in energy with $U_{\text{eff}} = 2$ eV. Similar energy gaps are observed as in the LSDA slab calculation, with the caveat that there is no gap in the majority O $2p$ states below the Fermi level; this is due to

a shift of the O $2p$ states from the Fermi level to lower energy when correlation is added. With a $U_{\text{eff}} = 2$ eV we find -100% spin-polarization at the Fermi level and a magnetic moment of $2.0 \mu_B$ per Ru atom. This effect on the magnetism with increased correlation is consistent with that found in the bulk calculations.

In summary, we never find a fully insulating ground state in our thin film calculations even in the presence of large correlation effects. We have also examined the layer-by-layer DOS for each slab (data not shown) and have not found an insulating surface layer in any of the calculations. However, as a result of the 2D confinement in the slabs, we do observe a narrowing of the minority t_{2g} bandwidth, and a shift of the Fermi level away from the band-center. Furthermore, with correlations the Fermi level also is seen to cut across the band-edge. These two properties together indicate that SrRuO_3 thin films are closer to a metal-insulator instability (with regards to the bulk), and consequently disorder is more likely to induce electron localization and form an insulating state. From these results we suggest the following two possibilities regarding the experimentally observed metal-insulator transition: (1) either the transition in SrRuO_3 thin films is not an intrinsic property of the system, but rather extrinsic and possibly due to surface roughness or defects from film deposition combined with the band narrowing from confinement and correlation; or (2) that SrRuO_3 thin films must be treated with more exotic electronic structure methods.

It is worth mentioning that PES experiments⁶¹ of SrRuO_3 films grown on SrTiO_3 substrates found a strong sensitivity of the t_{2g} spectral intensity and weight early in the deposition process (less than eight monolayers) with the intensity of the Ru $4d$ states becoming strongly enhanced above 15 monolayers. It was found that the film growth proceeds with a step terrace mechanism with minor atomic diffusion at less than five monolayers and followed by 3D island growth.⁷⁵ The disordered growth process should also reduce the stability of the ferromagnetic order, and due to poor percolation pathways, could contribute to the observed MI-transition concomitant with ferromagnetic ordering at less than five monolayers. The disorder at the surface has also recently been compared to that at the interface with the substrate (in this case SrTiO_3) with *in situ* PES techniques, and it was found that the sharp t_{2g} peak at the Fermi level is greatly suppressed at the surface, while it persists at the interface.⁷⁷ The decrease in itineracy due to the suppressed DOS at the Fermi level was also verified with surface and interface conductivity experiments. Since our calculations do not include any disordered surface configurations or non-stoichiometry, future first-principles calculations could clarify these competing interactions. We have however shown that neither strong correlations nor octahedral distortions, nor their combination are sufficient to reproduce the experimentally observed ultra-thin film metal-insulator transition.

V. CONCLUSIONS

We have examined the effects of structural distortions and correlation effects on the electronic and magnetic properties of SrRuO₃ with first-principles calculations. We find that by including weak strong-correlations with an effective Hubbard U of 0.6 eV or correction of the self-interaction error gives good agreement for bulk orthorhombic SrRuO₃ with the experimental spectroscopic data. The addition of the octahedral distortions leads to a narrowing of the majority spin Ru t_{2g} and O $2p$ states; however the exchange splitting is small with respect to these bandwidths and consequently a fully insulating ground state is not obtained. A half-metallic ground state was shown to be stable by including moderate electron-electron correlation effects $U > 2$ eV, which we note has not been observed experimentally.

The behavior of thin films was also examined in both cubic and orthorhombic unsupported films within the conventional LSDA approach and with weak correlations included. In neither case was the experimentally observed metal-insulator transition obtained. Since the electronic structures of surfaces are very sensitive to atomic reconstructions, we suggest that the experimentally observed metal-insulator transition could be a con-

sequence of extrinsic defects or an atomically disordered surface configuration.

Acknowledgments

We thank A. Fujimori for helpful discussions and bringing our attention to correlation characteristics in the spectroscopic data. The authors also thank A. Zayak, J. Neaton and W. Siemon for useful discussions and J. Okamoto and H. Kumigashira for providing us permission and use of the experimental PES data. This work was supported by the NSF under the grant NIRT 0609377 (NAS), by the SFI under the grant 07/IN.1/I945 (NC, SS) and by Seagate. JMR acknowledges support through a NDSEG fellowship sponsored by the DoD. Portions of this work made use of MRL Central Facilities supported by the MRSEC Program of the National Science Foundation under award No. DMR05-20415 and the CNSI Computer Facilities at UC Santa Barbara under NSF award No. CHE-0321368. Additional computational resources have been provided by the HEA IITAC project managed by the Trinity Center for High Performance Computing and by ICHEC.

-
- * Address correspondence to: nicola@mrl.ucsb.edu
- ¹ F. L. Marrec, A. Demuer, D. Jaccard, J.-M. Triscone, M. K. Lee, and C. B. Eom, *Appl. Phys. Lett.* **80**, 2338 (2002).
 - ² K. S. Takahashi, A. Sawa, Y. Ishii, H. Akoh, M. Kawasaki, and Y. Tokura, *Phys. Rev. B* **67**, 094413 (2003).
 - ³ W. J. Gallagher and S. S. P. Parkin, *IBM J. Res. Dev.* **50**, 5 (2006), ISSN 0018-8646.
 - ⁴ H. N. Lee, H. M. Christen, M. F. Chisholm, C. M. Rouleau, and D. H. Lowndes, *Appl. Phys. Lett.* **84**, 4107 (2004).
 - ⁵ C. H. Ahn, R. H. Hammond, T. H. Geballe, M. R. Beasley, J.-M. Triscone, M. Decroux, O. Fischer, L. Antognazza, and K. Char, *Appl. Phys. Lett.* **70**, 206 (1997).
 - ⁶ K. S. Takahashi, M. Gabay, D. Jaccard, K. Shibuya, T. Ohnishi, M. Lippmaa, and J.-M. Triscone, *Nature* **441**, 195 (2006).
 - ⁷ I. Zutic, J. Fabian, and S. D. Sarma, *Rev. Mod. Phys.* **76**, 323 (2005).
 - ⁸ D. Awschalom and M. Flatte, *Nature Phys.* **3**, 153 (2007).
 - ⁹ N. A. Spaldin and M. Fiebig, *Science* **309**, 391 (2005).
 - ¹⁰ R. Ramesh and N. A. Spaldin, *Nature Materials* **6**, 21 (2007).
 - ¹¹ A. Ohtomo, D. A. Muller, J. L. Grazul, and H. Y. Hwang, *Nature* **419**, 378 (2002).
 - ¹² A. Ohtomo and H. Y. Hwang, *Nature* **427**, 423 (2004).
 - ¹³ H. Y. Hwang, *Science* **313**, 1895 (2006).
 - ¹⁴ M. Huijben, G. Rijnders, D. H. A. Blank, S. Bals, S. V. Aert, J. Verbeeck, G. V. Tendeloo, A. Brinkman, and H. Hilgenkamp, *Nature Materials* **5**, 556 (2006).
 - ¹⁵ H. Yamada, Y. Ogawa, Y. Ishii, H. Sato, M. Kawasaki, H. Akoh, and Y. Tokura, *Science* **305**, 646 (2004).
 - ¹⁶ J. M. De Teresa, A. Barthélémy, A. Fert, J. P. Contour, F. Montaigne, and P. Seneor, *Science* **286**, 507 (1999).
 - ¹⁷ A. Brinkman, M. Huijben, M. van Zalk, J. Huijben, U. Zeitler, J. C. Maan, W. G. van der Wiel, G. Rijnders, D. H. A. Blank, and H. Hilgenkamp, *Nat. Mater.* **6**, 493 (2007).
 - ¹⁸ D. Toyota, I. Ohkuba, H. Kumigashira, M. Oshima, T. Ohnishi, M. Lippmaa, M. Takizawa, A. Fujimori, K. Ono, M. Kawasaki, et al., *Appl. Phys. Lett.* **87**, 162508 (2005).
 - ¹⁹ H.-D. Kim, H.-J. Noh, K. H. Kim, and S.-J. Oh, *Phys. Rev. Lett.* **93**, 126404 (2004).
 - ²⁰ J. Park, S.-J. Oh, J.-H. Park, D. M. Kim, and C.-B. Eom, *Phys. Rev. B* **69**, 085108 (2004).
 - ²¹ W. Siemons, G. Koster, A. Vailionis, H. Yamamoto, D. H. A. Blank, and M. R. Beasley, *Phys. Rev. B* **76**, 075126 (2007).
 - ²² P. B. Allen, H. Berger, O. Chauvet, L. Forro, T. Jarlborg, A. Junod, B. Revaz, and G. Santi, *Phys. Rev. B* **53**, 4393 (1996).
 - ²³ P. Kostic, Y. Okada, N. C. Collins, Z. Schlesinger, J. W. Reiner, L. Klein, A. Kapitulnik, T. H. Geballe, and M. R. Beasley, *Phys. Rev. Lett.* **81**, 2498 (1998).
 - ²⁴ G. Cao, S. McCall, M. Shepard, J. E. Crow, and R. P. Guertin, *Phys. Rev. B* **56**, 321 (1997).
 - ²⁵ K. Maiti, *Phys. Rev. B* **73**, 235110 (2006).
 - ²⁶ K. Maiti and R. S. Singh, *Phys. Rev. B* **71**, 161102(R) (2005).
 - ²⁷ H.-T. Jeng, S.-H. Lin, and C.-S. Hsue, *Phys. Rev. Lett.* **97**, 067002 (2006).
 - ²⁸ A. T. Zayak, X. Huang, J. B. Neaton, and K. M. Rabe, *Phys. Rev. B* **74**, 094104 (2006).
 - ²⁹ V. M. Goldschmidt, *Naturwissenschaften* **14**, 477 (1926).
 - ³⁰ N. Fukunaga and N. Tsuda, *J. Phys. Soc. Jpn.* **63**, 3798

- (1994).
- ³¹ A. Kanbayasi, J. Phys. Soc. Jpn. **41**, 1876 (1976).
 - ³² D. J. Singh, J. Appl. Phys. **79**, 4818 (1996).
 - ³³ I. I. Mazin and D. J. Singh, Phys. Rev. B **56**, 2556 (1997).
 - ³⁴ G. Santi and T. Jarlborg, J. Phys.: Condens. Matter **9**, 9563 (1997).
 - ³⁵ W. Kohn and L. J. Sham, Phys. Rev. **140**, A1133 (1965).
 - ³⁶ J. M. Soler, E. Artacho, J. D. Gale, A. García, J. Junquera, P. Ordejón, and D. Sánchez-Portal, J. Phys.: Condens. Matter **14**, 2745 (2002).
 - ³⁷ D. Sánchez-Portal, P. Ordejón, E. Artacho, and J. M. Soler, Int. J. Quant. Chem. **65**, 453 (1997).
 - ³⁸ P. Ordejón, E. Artacho, and J. M. Soler, Phys. Rev. B **53**, R10441 (1996).
 - ³⁹ G. Kresse and J. Furthmüller, Phys. Rev. B **54**, 11169 (1996).
 - ⁴⁰ G. Kresse and D. Joubert, Phys. Rev. B **59**, 1758 (1999).
 - ⁴¹ J. P. Perdew and A. Zunger, Phys. Rev. B **23**, 5048 (1981).
 - ⁴² D. M. Ceperley and B. J. Alder, Phys. Rev. Lett. **45**, 566 (1980).
 - ⁴³ P. E. Blöchl, Phys. Rev. B **50**, 17953 (1994).
 - ⁴⁴ H. J. Monkhorst and J. D. Pack, Phys. Rev. B **13**, 5188 (1976).
 - ⁴⁵ P. E. Blöchl, O. Jepsen, and O. K. Andersen, Phys. Rev. B **49**, 16223 (1994).
 - ⁴⁶ L. Kleinman and D. M. Bylander, Phys. Rev. Lett. **48**, 1425 (1982).
 - ⁴⁷ N. Troullier and J. L. Martins, Phys. Rev. B **43**, 1993 (1991).
 - ⁴⁸ B. C. Chakoumakos, S. E. Nagler, S. T. Mixture, and H. M. Christen, Physica B Condensed Matter **241**, 358 (1998).
 - ⁴⁹ V. I. Anisimov, F. Aryasetiawan, and A. I. Liechtenstein, J. Phys.: Condens. Matter **9**, 767 (1997).
 - ⁵⁰ S. L. Dudarev, G. A. Botton, S. Y. Savrasov, C. J. Humphreys, and A. P. Sutton, Phys. Rev. B **57**, 1505 (1998).
 - ⁵¹ A. G. Petukhov, I. I. Mazin, L. Chioncel, and A. I. Liechtenstein, Phys. Rev. B **67**, 153106 (2003).
 - ⁵² A. Filippetti and N. A. Spaldin, Phys. Rev. B **67**, 125109 (2003).
 - ⁵³ D. Vogel, P. Krüger, and J. Pollmann, Phys. Rev. B **54**, 5495 (1996).
 - ⁵⁴ C. D. Pemmaraju, T. Archer, D. Sánchez-Portal, and S. Sanvito, Phys. Rev. B **75**, 045101 (2007).
 - ⁵⁵ M. Stengel and N. A. Spaldin, Phys. Rev. B **77**, 155106 (2008).
 - ⁵⁶ C. W. Jones, P. D. Battle, P. Lightfoot, and W. T. A. Harrison, Acta Cryst. C **45**, 365 (1989).
 - ⁵⁷ J. Okamoto, T. Mizokawa, A. Fujimori, I. Hase, M. Nohara, H. Takagi, Y. Takeda, and M. Takano, Phys. Rev. B **60**, 2281 (1999).
 - ⁵⁸ K. Fujioka, J. Okamoto, T. Mizokawa, A. Fujimori, I. Hase, M. Abbate, H. J. Lin, C. T. Chen, Y. Takeda, and M. Takano, Phys. Rev. B **56**, 6380 (1997).
 - ⁵⁹ J. Okamoto (2008), unpublished data on new samples. The material preparation and characterization follows that outlined in J. Okamoto *et al.*, Phys. Rev. B **60**, 2281 (1999).
 - ⁶⁰ Reused with permission from D. Toyota, Appl. Phys. Lett. **87** 162508 (2005). Copyright 2005, American Institute of Physics.
 - ⁶¹ J. Kim, J. Chung, and S.-J. Oh, Phys. Rev. B **71**, 121406(R) (2005).
 - ⁶² G. Herranz, N. Dix, F. Sánchez, B. Martínez, J. Fontcuberta, M. V. García-Cuenca, C. Ferrater, M. Varela, D. Hrabovsky, and A. R. Fert, J. Appl. Phys. **97**, 10M321 (2005).
 - ⁶³ D. C. Worledge and T. H. Geballe, Phys. Rev. Lett. **85**, 5182 (2000).
 - ⁶⁴ I. I. Mazin, Phys. Rev. Lett. **83**, 1427 (1999).
 - ⁶⁵ J. M. D. Coey and S. Sanvito, Journal of Physics D: Applied Physics **37**, 988 (2004).
 - ⁶⁶ A. F. Andreev, Sov. Phys. JETP **19**, 1228 (1964).
 - ⁶⁷ J. Soulen, R. J., J. M. Byers, M. S. Osofsky, B. . Nadgorny, T. Ambrose, S. F. Cheng, P. R. Broussard, C. T. Tanaka, J. N owak, J. S. Moodera, et al., Science **282**, 85 (1998).
 - ⁶⁸ S. K. Upadhyay, A. Palanisami, R. N. Louie, and R. A. Buhrman, Phys. Rev. Lett. **81**, 3247 (1998).
 - ⁶⁹ P. Raychaudhuri, A. P. Mackenzie, J. W. Reiner, and M. R. Beasley, Phys. Rev. B **67**, 020411(R) (2003).
 - ⁷⁰ B. Nadgorny, M. S. Osofsky, D. J. Singh, G. T. Woods, J. R. J . Soulen, M. K. Lee, S. D. Bu, and C. B. Eom, Appl. Phys. Lett. **82**, 427 (2003).
 - ⁷¹ J. Sanders, G. T. Woods, P. Poddar, H. Srikanth, B. D. ski, and S. Kolesnik, 49th Annual Conference on Magnetism and Magnetic Materials **97**, 10C912 (2005).
 - ⁷² A. R. Rocha, V. M. Garcia-Suarez, S. Bailey, C. Lambert, J. Ferrer, and S. Sanvito, Phys. Rev. B **73**, 085414 (2006).
 - ⁷³ F. Taddei, S. Sanvito, and C. Lambert, Journal of Low Temperature Physics **124**, 305 (2001).
 - ⁷⁴ G. Rijnders, D. H. A. Blank, J. Choi, and C.-B. Eom, Appl. Phys. Lett. **84**, 505 (2004).
 - ⁷⁵ D. Toyota, I. Ohkubo, H. Kumigashira, M. Oshima, T. Ohnishi, M. Lippmaa, M. Kawasaki, and H. Koinuma, J. Appl. Phys. **99**, 08N505 (2006).
 - ⁷⁶ Q. Gan, R. A. Rao, C. B. Eom, J. L. Garrett, and M. Lee, Appl. Phys. Lett. **72**, 978 (1998).
 - ⁷⁷ H. Kumigashira, M. Minohara, M. Takizawa, A. Fujimori, D. Toyota, I. Ohkubo, M. Oshima, M. Lippmaa, and M. Kawasaki, Appl. Phys. Lett. **92**, 122105 (2008).
 - ⁷⁸ We used 10 valence electrons for Sr ($4s^2 4p^6 5s^2$), 14 for Ru ($4p^6 4d^7 5s^1$), and 6 for each oxygen ($2s^2 2p^4$).
 - ⁷⁹ The electronic configurations for each atom is: Sr $4s^2 4p^6 4d^0 4f^0$ (1.50, 1.50, 2.00, 2.00), Ru $4s^2 4p^6 4d^7 4f^0$ (1.30, 1.30, 1.40, 1.30), and O $2s^2 2p^4 3d^0 4f^0$ (1.15, 1.15, 1.15, 1.50), where the cutoff radii for each orbital is given in parentheses.
 - ⁸⁰ The grid cutoff mentioned is not directly comparable to the plane-wave cutoff value used to represent the wavefunctions in a standard plane-wave implementation of DFT, it is rather used here to represent the density, and is typically four times larger than the wavefunction cutoff.
 - ⁸¹ Although in this symmetry the RuO₆ cages are rotated, we retain the standard spherical harmonics for the 4d orbitals described in terms of a octahedral crystal field for a cubic perovskite. The transformation from the cubic to orthorhombic *d* orbital reference frame requires a rotation of $\pi/4$ about the [001]-direction; additionally, the octahedral units retain almost all of their integrity, i.e. the apical and axial Ru-O bond lengths are identical within 0.01 Å.
 - ⁸² The Brillouin zone was sampled in these cases with a $20 \times 20 \times 1$ Monkhorst-Pack mesh for the orthorhombic structure and a $40 \times 40 \times 1$ mesh for the cubic structure.
 - ⁸³ Complete structural relaxation of the three unit cell slab within the orthorhombic symmetry did not produce significant changes in the electronic or magnetic structure.